

TECHNICAL DATA SHEET

VANTABLACK[®]

310


Vantablack[®] 310 Ultra-black Aerospace Coating



PRODUCT DESCRIPTION

Vantablack 310 is an ultra-black coating for terrestrial and space applications, offering 2% Total Hemispherical Reflectance. It is engineered for stray light suppression, thermal management, and optical shielding. Spray-applied coating suitable for both manual and automated systems. Handleable finish with a robust surface for integration and assembly.

Table 1: Typical Optical Properties of Vantablack 310	
SURFACE APPEARANCE	Matte Ultra-black
TOTAL HEMISPHERICAL REFLECTANCE	
(220 – 1400nm)	~ 2%
(2 – 8 µm)	< 2%
BRDF	Near Lambertian
EMISSIONIVITY	0.98

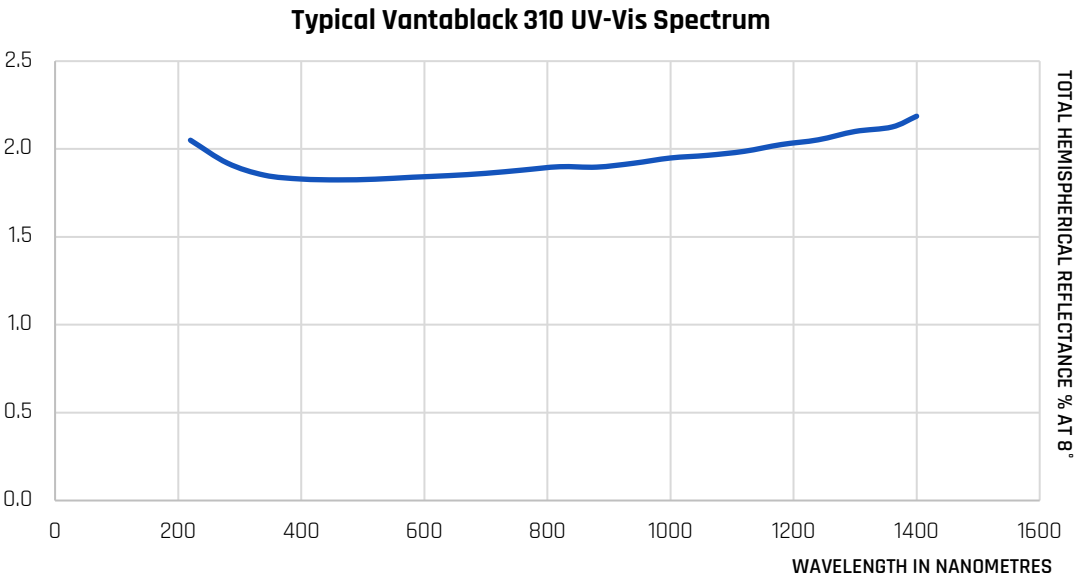

Typical Vantablack 310 IR Spectrum

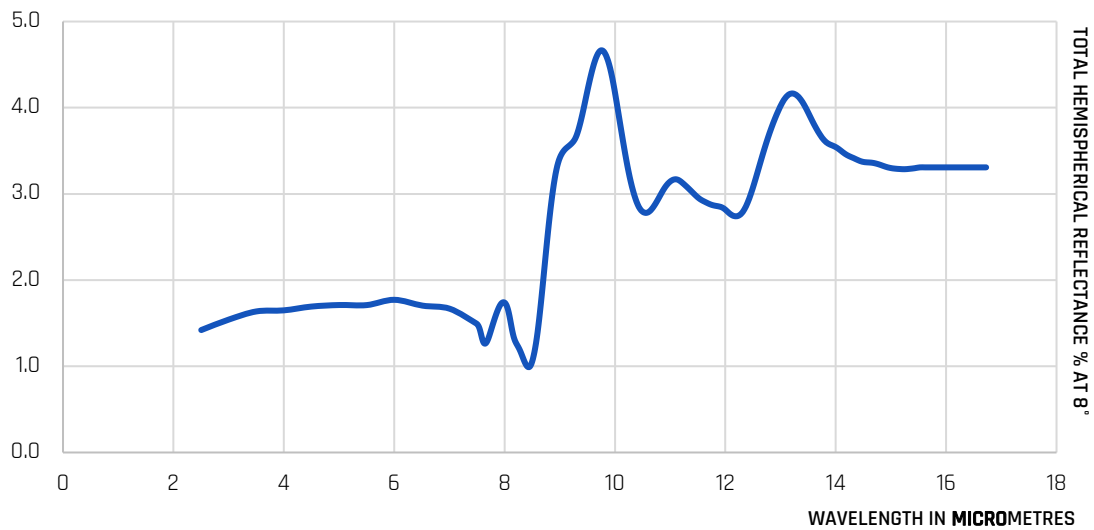


Table 2: Typical Physical Properties of Vantablack 310

OUTGASSING (ASTM E595-77)	
%TML	< 1.0
%CVC	< 0.1
ATOMIC OXYGEN (After equivalent of 3 years in LEO RAM facing*)	
%TML	7.2
%THR	2.8
SHEET RESISTANCE Ω/\square	$10^3 - 10^4$
OPERATIONAL TEMPERATURE RANGE	-196 - 200 °C
COATING MASS (mg/cm ²)	< 5
COATING THICKNESS (μm)	30
ADHESION (ISO 2409)	Grade 1
HARDNESS (ISO 15184)	9H

*Fluence 10²¹ atom/cm²

PACKAGING INFORMATION

Available in 475mL (1 pint) and 4 litre (1.05 gallon) container.



SURFACE PREPARATION

Vantablack 310 should be applied to surfaces that are clean, dry and free from loosely adhering materials and grease. Vantablack 310 can be directly applied to most substrates. For some substrates the use of standard pre-treatments may be recommended. Contact your Vantablack representative for additional information.


Table 3: Typical Properties of Vantablack 310

THEORETICAL COVERAGE (100% Transfer efficiency @ 30µm DFT)	
m ² /l	10
VOLATILE ORGANIC COMPOUND (VOC)	
g/litre	485
SOLIDS CONTENT (ASTM D2369-87)	
% by weight	43
DENSITY (ASTM D1475-85)	
kg/litre	0.97
FLASH POINT (ASTM D3278-82 closed cup)	
310 Base	-16°C
310 Catalyst	40°C



MIXING


Vantablack 310 is a two-component paint system. The base requires agitation before catalyst addition. The base can be agitated on a paint shaker for 5 minutes or stirred/shaken vigorously until the paint is homogeneous and there is no settling.



CATALYST ADDITION

Add Vantablack 310 catalyst to premixed Vantablack 310 base in a ratio 25mL catalyst to 1L base.

The catalyst must be thoroughly mixed through the base and passed through a 260 µm filter prior to application.



APPLICATION

Vantablack 310 is typically applied using conventional spray systems. It can be applied manually or using an automated system for high volume components. The product can be sprayed as supplied but up to 10% Vantablack 001 thinners can be used.

Recommended dry film thickness is 30µm (1.2 mils). Hold the spray gun perpendicular to the surface. Overlap the spray pattern and apply a typical wet film to achieve full coverage.

Below conditions are a known starting configuration and should be used as a guide only.

SPRAYING PARAMETERS	
Needle/nozzle size	1.2 mm
Air cap	TE10
Spray pressure	2-3 bar
Fluid flow	120 mL/min
Spraying gas	Dry nitrogen or compressed dry air*
Spraying temperature	10 – 25°C
Spraying Humidity	RH < 75%

Vantablack 310 typically requires 1 pass applied perpendicular to the surface.

Distance to substrate	75 mm
Traverse speed	40 mm/min

Vantablack 310 can be applied by immersion coating and/or brush/roller application. Contact your Vantablack representative for additional information.

Clean equipment immediately after use with Vantablack 001 thinners.



CURING

Vantablack 310 will cure in ambient conditions. The cure is dependent on relative humidity (min. 40%) and temperature (min. 10°C).

	TIME	TEMPERATURE	RELATIVE HUMIDITY
Ambient cure	2 hours	21°C	50%
Accelerated cure	30 minutes	35°	50%

Vantablack 310 will rapidly cure in 30 minutes at 50% humidity and 35°C.



BAKING

For full outgassing performance a bakeout step is required at 120°C for 30 minutes.



RECOAT

Before recoating Vantablack 310 must be cured and the surface prepared by abrading the surface and wiping with Vantablack 001 thinners.



STORAGE/POT LIFE

Vantablack 310 Base

Unopened shelf life 6 months from manufacturing date kept within 0°C to +25°C. Store away from heat, sparks and flames.

Vantablack 310 Catalyst

Unopened shelf life 24 months from manufacturing date kept within 0°C to +25°C. Store away from heat, sparks and flames.

Catalysed paint has a 48-hour pot life if stored under nitrogen or clean dry air.

Contamination with moisture will initiate curing.



SAFETY INFORMATION

Before using any Vantablack product, refer to the Material Safety Data Sheet (MSDS) for safe use and handling instructions.

For industrial and commercial use only. Must be handled and applied by trained personnel.



CLEANING THE SURFACE

If the surface needs to be handled, we recommend the use of powder free nitrile/latex gloves. This avoids skin contamination of the ultra-black surface during the handling or assembly process.

Skin contact risks leaving fingerprints or residues that may impair the optical performance.

The surface can be washed with solvent (acetone, ethyl acetate or IPA) and wiped with a lint free cloth.



TECHNICAL SUPPORT

For further technical support please contact:

- technicalsupport@surreynanosystems.com